arXiv:cond-mat/0003249v1 [cond-mat.str-el] 14 Mar 2000

Electromagnetic Response of a $k_x \pm ik_y$ Superconductor: Effect of Order Parameter Collective Modes

S. Higashitani and K. Nagai

Faculty of Integrated Arts and Sciences, Hiroshima University, Kagamiyama 1-7-1, Higashi-hiroshima 739-8521, Japan

(February 1, 2008)

Effects of order parameter collective modes on electromagnetic response are studied for a clean spin-triplet superconductor with $k_x \pm ik_y$ orbital symmetry, which has been proposed as a candidate pairing symmetry for Sr_2RuO_4. It is shown that the $k_x \pm ik_y$ superconductor has characteristic massive collective modes analogous to the clapping mode in the A-phase of superfluid ^{3}He. We discuss the contribution from the collective modes to ultrasound attenuation and electromagnetic absorption. We show that in the electromagnetic absorption spectrum the clapping mode gives rise to a resonance peak well below the pair breaking frequency, while the ultrasound attenuation is hardly influenced by the collective excitations.

74.25.Nf, 74.40.+k

Superconducting and superfluid properties of unconventional Cooper pairing states continue to be of interest in the research of strongly correlated fermion systems such as liquid ^{3}He, heavy fermion compounds, high-T_c superconductors and the more recently discovered superconductor Sr_2RuO_4.[1] The spin-triplet $k_x \pm ik_y$-wave state is an example of the unconventional pairing states and is known to describe the superfluidity of ^{3}He-A. Two-dimensional (2D) version of this state has recently attracted much attention as a candidate pairing state for Sr_2RuO_4.

The possibility of the spin-triplet p-wave pairing in Sr_2RuO_4 was first suggested by Rice and Sigrist[2] from the analogy to ^{3}He. There now exist considerable experimental evidences supporting the unconventional spin-triplet superconductivity in Sr_2RuO_4. The absence of the Hebel-Slichter peak in $1/T_1$[3] and substantial reduction in T_c by non-magnetic impurities[4] indicate that Sr_2RuO_4 is at least not a conventional s-wave superconductor. The μSR experiments[5] suggest a pairing state with broken time reversal symmetry. More strong evidence of the triplet pairing has been found by ^{17}O NMR measurements[6] in which the temperature-independent Knight shift is observed for magnetic fields parallel to the RuO_2 plane. Possible pairing states in Sr_2RuO_4 have been classified from a group theoretical point of view.[2] It was shown that the quasi-2D electronic structure of Sr_2RuO_4 leads to five possible p-wave states stabilized by the absence of gap nodes. Among these states, the pairing state compatible with all the above experiments is the $k_x \pm ik_y$ state which is the 2D analog of ^{3}He-A.

Study of the electromagnetic (EM) response provides valuable information on the properties of unconventional superconductors. Dynamical properties are, in particular, intriguing because they depend not only on the equilibrium gap structure but also on the collective excitations of the order parameter.[7,8] As is known in the study of superfluid ^{3}He, internal degrees of freedom of the order parameter give rise to the order parameter collective modes (OPCM's) specific to a given pairing symmetry. In this paper, we discuss, within the collisionless regime, how the OPCM's in the $k_x \pm ik_y$ superconductor contribute to the EM response.

The OPCM's in the 2D $k_x \pm ik_y$ state has been discussed by Tewordt.[9,10] As in the case of ^{3}He-A, there exists the clapping mode, which is a characteristic massive collective mode resulting from the orbital degrees of freedom of the $k_x \pm ik_y$-wave order parameter. Tewordt showed that the coupling of this mode to external fields vanishes in the long wavelength limit $(q \to 0)$[10] and so he did not attempt to discuss the observability of the clapping mode. The effect of a finite wave vector $\mathbf{q}$ is, however, important even in type II superconductors when we consider the role of OPCM's in the EM response. We in fact show in this paper, by calculating a q-dependent dynamical conductivity, that the clapping mode leads to an EM absorption peak. We also discuss the ultrasound attenuation. We show that, although ultrasound experiments have played a key role in the study of the OPCM's in ^{3}He, the ultrasound cannot be a good probe of the OPCM's in metals such as Sr_2RuO_4. This is because the sound velocity in ordinary metals is much smaller than the Fermi velocity v_{F}, in contrast to ^{3}He.

The 2D $k_x \pm ik_y$ state is defined on a cylindrical Fermi surface and the orbital structure of the order parameter is expressed in terms of two basis functions $\hat{k}_x = \cos\theta$ and $\hat{k}_y = \sin\theta$ specifying the direction of the Fermi momentum $\mathbf{k}_{\mathrm{F}}$. The matrix order parameter is given by

$$\hat{\Delta}_{\mathbf{k}} = \Delta(\hat{k}_x \pm i\hat{k}_y)\sigma_z i\sigma_y = \Delta e^{\pm i\theta}\sigma_z i\sigma_y, \qquad (1)$$

where σ_i's are Pauli matrices. The gap $(\hat{\Delta}_{\mathbf{k}}\hat{\Delta}_{\mathbf{k}}^{\dagger})^{1/2} = \Delta$ of the two unitary states is independent of $\mathbf{k}$ and the Bogoliubov-quasiparticle energy $E_{\mathbf{k}} = (\xi_{\mathbf{k}}^2 + \hat{\Delta}_{\mathbf{k}}\hat{\Delta}_{\mathbf{k}}^{\dagger})^{1/2}$ is the same as that of the s-wave state.

The collective excitations of the order parameter are described as oscillations of order parameter fluctuations from the equilibrium state. In the $k_x \pm ik_y$ state, one of the two degenerate states is realized in equilibrium. We choose the $k_x + ik_y$ state as the equilibrium state and consider an order parameter fluctuation of a plane wave form $\delta\hat{\Delta}_{\mathbf{k}}(\mathbf{q},\omega)e^{i(\mathbf{q}\cdot\mathbf{r}-\omega t)}$. Such fluctuation can be excited by space-time dependent EM fields, a scalar potential $\phi(\mathbf{q},\omega)e^{i(\mathbf{q}\cdot\mathbf{r}-\omega t)}$ and a vector potential $\mathbf{A}(\mathbf{q},\omega)e^{i(\mathbf{q}\cdot\mathbf{r}-\omega t)}$. The order parameter fluctuation is expressed using the two bases $e^{\pm i\theta}=\hat{k}_x\pm i\hat{k}_y$ as

$$\delta\hat{\Delta}_{\mathbf{k}}(\mathbf{q},\omega)=[D_+(\mathbf{q},\omega)e^{i\theta}+D_-(\mathbf{q},\omega)e^{-i\theta}]\sigma_z i\sigma_y, \quad (2)$$

where D_+ and D_- are variables to be determined by the self-consistency equation. Since D_+ and D_- are complex variables, there are four degrees of freedom of the order parameter fluctuations in the representation of (2).

A well-established way to study the dynamical properties including the fluctuations of the order parameter is to introduce matrix distribution functions in spin space, $n_{\mathbf{k}}(\mathbf{q},\omega)$ and $f_{\mathbf{k}}(\mathbf{q},\omega)$ with matrix elements $(n_{\mathbf{k}})_{\alpha\beta}=\int dt\, e^{-i\omega t}\langle a^\dagger_{\mathbf{k}_-\beta}a_{\mathbf{k}_+\alpha}\rangle$ and $(f_{\mathbf{k}})_{\alpha\beta}=\int dt\, e^{-i\omega t}\langle a_{-\mathbf{k}_-\beta}a_{\mathbf{k}_+\alpha}\rangle$ ($\mathbf{k}_\pm=\mathbf{k}\pm\mathbf{q}/2$). The deviation $\delta f_{\mathbf{k}}$ of $f_{\mathbf{k}}$ from its equilibrium value determines the order parameter fluctuation via the self-consistency equation:

$$\delta\hat{\Delta}_{\mathbf{k}}(\mathbf{q},\omega)=\sum_{\mathbf{k}'}v_{\mathbf{k},\mathbf{k}'}\delta f_{\mathbf{k}'}(\mathbf{q},\omega), \quad (3)$$

where $v_{\mathbf{k},\mathbf{k}'}=-2g_1\hat{\mathbf{k}}\cdot\hat{\mathbf{k}}'$ is the pairing interaction. The deviation $\delta n_{\mathbf{k}}$ is related to the charge current density as

$$\mathbf{J}(\mathbf{q},\omega)=ev_{\mathrm{F}}\sum_{\mathbf{k}}\hat{\mathbf{k}}\mathrm{Tr}\,\delta n_{\mathbf{k}}(\mathbf{q},\omega)-\frac{ne^2}{mc}\mathbf{A}(\mathbf{q},\omega), \quad (4)$$

where n is the number density. (Note that for the spin-independent perturbations considered here, $\delta n_{\mathbf{k}}$ is proportional to the unit matrix and thus the trace in Eq. (4) gives only a factor 2.) The distribution functions have been intensively studied in the context of ultrasound attenuation in superfluid ^{3}He (see, for a review, Ref. 12). Assuming the particle-hole symmetry, we can write the distribution functions integrated over the energy variable $\xi_{\mathbf{k}}$ as

$$\begin{aligned}\int_{-\infty}^{\infty}d\xi_{\mathbf{k}}\delta n_{\mathbf{k}}&=(\delta\epsilon_0+\delta\epsilon_1)\eta/(\omega-\eta)\\&\quad-2\mathcal{F}\hat{\Delta}_{\mathbf{k}}\hat{\Delta}^\dagger_{\mathbf{k}}(\omega\delta\epsilon_0+\eta\delta\epsilon_1)/(\omega-\eta)\\&\quad+\frac{\mathcal{F}}{2}(\omega+\eta)(\delta\hat{\Delta}_{\mathbf{k}}\hat{\Delta}^\dagger_{\mathbf{k}}-\hat{\Delta}_{\mathbf{k}}\delta\hat{\Delta}^\dagger_{\mathbf{k}}), \quad (5)\end{aligned}$$

$$\begin{aligned}\int_{-\infty}^{\infty}d\xi_{\mathbf{k}}\delta f_{\mathbf{k}}&=\int_{-\varepsilon_c}^{\varepsilon_c}d\xi_{\mathbf{k}}\frac{\Theta_{\mathbf{k}}}{E_{\mathbf{k}}}\delta\hat{\Delta}_{\mathbf{k}}\\&\quad-\mathcal{F}\Big[\frac{1}{2}(\omega^2-2\hat{\Delta}_{\mathbf{k}}\hat{\Delta}^\dagger_{\mathbf{k}}-\eta^2)\delta\hat{\Delta}_{\mathbf{k}}\\&\qquad-\hat{\Delta}_{\mathbf{k}}\delta\hat{\Delta}^\dagger_{\mathbf{k}}\hat{\Delta}_{\mathbf{k}}-(\omega\delta\epsilon_0+\eta\delta\epsilon_1)\hat{\Delta}_{\mathbf{k}}\Big], \quad (6)\end{aligned}$$

where $\delta\epsilon_0=e\phi(\mathbf{q},\omega)$ and $\delta\epsilon_1=-(e/mc)\mathbf{k}_{\mathrm{F}}\cdot\mathbf{A}(\mathbf{q},\omega)$ represent the perturbation energies, $\eta=\mathbf{v}_{\mathrm{F}}\cdot\mathbf{q}$, $\Theta_{\mathbf{k}}=-(1/2)\tanh(E_{\mathbf{k}}/2T)$, ε_c is the usual cutoff energy and

$$\mathcal{F}=\int_{-\infty}^{\infty}\frac{d\xi_{\mathbf{k}}}{2E_{\mathbf{k}_+}E_{\mathbf{k}_-}}\Big[\frac{(E_{\mathbf{k}_+}+E_{\mathbf{k}_-})(\Theta_{\mathbf{k}_-}+\Theta_{\mathbf{k}_+})}{\omega^2-(E_{\mathbf{k}_+}+E_{\mathbf{k}_-})^2}+\frac{(E_{\mathbf{k}_+}-E_{\mathbf{k}_-})(\Theta_{\mathbf{k}_-}-\Theta_{\mathbf{k}_+})}{\omega^2-(E_{\mathbf{k}_+}-E_{\mathbf{k}_-})^2}\Big]. \quad (7)$$

Here we have dropped the arguments $\mathbf{q}$ and ω for brevity ($\delta\hat{\Delta}^\dagger=\delta\hat{\Delta}^\dagger(-\mathbf{q},-\omega)$). In Eqs. (5) and (6), small corrections of order q/k_{F} have been neglected and accordingly $\hat{\Delta}_{\mathbf{k}_\pm}$ has been put as $\hat{\Delta}_{\mathbf{k}}$.[11]

Now we discuss the OPCM's in the k_x+ik_y state. It is convenient to introduce the following new variables:

$$\frac{1}{2}[D_+(\mathbf{q},\omega)\pm D_+^*(-\mathbf{q},-\omega)]=\begin{cases}D'_+\\D''_+\end{cases}, \quad (8)$$

$$\frac{1}{2}[D_-(\mathbf{q},\omega)e^{-2i\theta_q}\pm D_-^*(-\mathbf{q},-\omega)e^{2i\theta_q}]=\begin{cases}D'_-\\D''_-\end{cases}, \quad (9)$$

where $e^{i\theta_q}=\hat{q}_x+\mathrm{i}\hat{q}_y$. Using Eq. (6), the self-consistency equation (3) can be written in terms of these variables as

$$M_1\begin{pmatrix}D'_+\\D'_-\end{pmatrix}=\begin{pmatrix}0\\2i\Delta\langle\mathcal{F}(\omega\delta\epsilon_0+\eta\delta\epsilon_1)\sin2\vartheta\rangle_{\mathbf{k}}\end{pmatrix}, \quad (10)$$

$$M_2\begin{pmatrix}D''_+\\D''_-\end{pmatrix}=\begin{pmatrix}2\Delta\langle\mathcal{F}(\omega\delta\epsilon_0+\eta\delta\epsilon_1)\rangle_{\mathbf{k}}\\2\Delta\langle\mathcal{F}(\omega\delta\epsilon_0+\eta\delta\epsilon_1)\cos2\vartheta\rangle_{\mathbf{k}}\end{pmatrix}, \quad (11)$$

where ϑ is the angle between $\mathbf{k}$ and $\mathbf{q}$, $\langle\cdots\rangle_{\mathbf{k}}$ denotes the angle average over the Fermi surface and $M_{1,2}$ are 2×2 matrices with the following elements:

$$\begin{aligned}&(M_1)_{11}=\langle\mathcal{F}(\omega^2-4\Delta^2-\eta^2)\rangle_{\mathbf{k}},\\&(M_1)_{22}=\langle\mathcal{F}[\omega^2-2\Delta^2(1+\cos4\vartheta)-\eta^2]\rangle_{\mathbf{k}},\\&(M_1)_{12}=(M_1)_{21}=\langle\mathcal{F}(\omega^2-4\Delta^2-\eta^2)\cos2\vartheta\rangle_{\mathbf{k}},\\&(M_2)_{11}=\langle\mathcal{F}(\omega^2-\eta^2)\rangle_{\mathbf{k}},\\&(M_2)_{22}=\langle\mathcal{F}[\omega^2-2\Delta^2(1-\cos4\vartheta)-\eta^2]\rangle_{\mathbf{k}},\\&(M_2)_{12}=(M_2)_{21}=\langle\mathcal{F}(\omega^2-\eta^2)\cos2\vartheta\rangle_{\mathbf{k}}. \quad (12)\end{aligned}$$

Note that the variables D' and D'' are decoupled from each other.

The OPCM's correspond to the eigen modes in the absence of external fields. The eigen frequencies ω are therefore determined by $\det M_{1,2}=0$. In the long wavelength limit, $q\to0$, it is easy to obtain the eigen frequencies. In this limit, since the off-diagonal elements of $M_{1,2}$ may be neglected, all the modes decouple. The results for $q\to0$ are summarized in Table I. The D'_+-mode has the eigen frequency just at the pair breaking edge, $\omega=2\Delta$. The variable D''_+ represents a mode corresponding to the phase fluctuation of the order parameter, namely, the so-called Anderson-Bogoliubov mode. This is a gapless mode with sound-like dispersion $\omega=(v_{\mathrm{F}}/\sqrt{2})q$ but is replaced by a plasmon when the Coulomb interaction between electrons is taken into account.[7] The remaining two modes, D_--modes, have the same character as the clapping mode in superfluid ^{3}He-A.[12,13] The eigen frequency of the clapping modes in the 2D system is $\omega=\sqrt{2}\Delta$ and is below the pair breaking energy 2Δ. At finite q, the dispersion relation of the clapping modes up to the order q^2 is given by

$$\omega_{\mathrm{cl}}^2(q)=2\Delta^2+\frac{1}{2}(v_{\mathrm{F}}q)^2. \quad (13)$$

The coupling of the OPCM's to the external fields is determined by the right-hand side of Eqs. (10) and (11). We see that the $D'_\pm$-modes and the $D''_\pm$-modes couple to the transverse field and the longitudinal field, respectively.

The presence of the coupling between the $D''_\pm$-modes and the longitudinal field means that these modes can be excited by a longitudinal phonon field. Since the collective excitations couple to the density fluctuation $\delta\rho(\mathbf{q},\omega) = \sum_{\mathbf{k}} \mathrm{Tr}\, \delta n_{\mathbf{k}}$ via the last term in Eq. (5), there is a possibility that the clapping mode (D''_--mode) is observed by ultrasound measurements. We have estimated the ultrasound attenuation coefficient by assuming typical conditions $\omega \ll v_{\mathrm{F}} q \ll \Delta$ for ultrasound measurements in ordinary metals and also in $\mathrm{Sr_2RuO_4}$. (In $\mathrm{Sr_2RuO_4}$, the sound velocity is $\sim 10^5$ cm/s[14], the Fermi velocity is $\sim 10^7$ cm/s[15,16] and $\Delta \sim 1$ K.) The attenuation coefficient from quasiparticle excitations coincides with that for the s-wave superconductor because of the isotropic gap. The contribution from the collective excitations can be obtained using Eqs. (5) and (11). Taking into account the above conditions and considering the limit $\omega \to 0$, one can find, after straightforward algebra, that the collective excitations give only a small correction of order $(\omega/v_{\mathrm{F}} q)^2 \sim 10^{-4}$ to the quasiparticle contribution. Consequently, the ratio of the superconducting to normal attenuation coefficient in the low-frequency limit $\omega \to 0$ is given by the well-known BCS result $\alpha_s/\alpha_n = 2/(e^{\Delta/T}+1)$. Thus sound waves are not suitable probe for the OPCM. It is to be noted that, in contrast to ordinary metals, ultrasound propagation in superfluid ^{3}He is in the high frequency regime such that $\omega \sim \Delta \gg v_{\mathrm{F}} q$ where the OPCM plays an important role. This is a reason why sound waves can be a good probe of the OPCM's in superfluid ^{3}He.

Now we consider the transverse response of a $k_x + ik_y$ superconductor. The transverse response is conveniently described by the complex conductivity $\sigma_t(\mathbf{q},\omega)$ for the transverse electric field $E_t(\mathbf{q},\omega) = (i\omega/c)A_t(\mathbf{q},\omega)$. The real part σ_1 of the complex conductivity $\sigma_t = \sigma_1 + i\sigma_2$ determines the absorption of EM waves. We can readily obtain σ_t by calculating the transverse current density using the above formulation. The conductivity consists of three characteristic parts, i.e., $\sigma_t = \sigma_t^{\mathrm{qp}} + \sigma_t^{\mathrm{cm}} + \sigma_t^{\mathrm{dia}}$; the first and the second terms are contributions from quasiparticle excitations and from collective modes, respectively, and the last term $\sigma_t^{\mathrm{dia}} = ine^2/m\omega$ arises from the diamagnetic current $(-ne^2/mc)A_t$. The quasiparticle contribution σ_t^{qp} is the same as the BCS result for the s-wave superconductor:

$$\sigma_t^{\mathrm{qp}}(\mathbf{q},\omega) = \frac{2ine^2}{m\omega} \langle \frac{\hat{k}_t^2 \eta^2}{\omega^2 - \eta^2}(1 - 2\Delta^2 \mathcal{F}) \rangle_{\mathbf{k}}, \qquad (14)$$

where $\hat{k}_t = \sin\vartheta$ is the transverse component of the unit vector $\hat{\mathbf{k}}$. The collective-mode contribution σ_t^{cm} comes only from the D'_--clapping mode and is obtained as

$$\begin{aligned} \sigma_t^{\mathrm{cm}}(\mathbf{q},\omega) &= -2iev_{\mathrm{F}}\Delta \sum_{\mathbf{k}} \hat{k}_t \eta \mathcal{F} \sin 2\vartheta D'_-/E_t \\ &= \frac{4ine^2}{m\omega} \frac{\Delta^2 \langle \mathcal{F}(\omega^2 - 4\Delta^2 - \eta^2)\rangle_{\mathbf{k}} \langle \mathcal{F}\eta \hat{k}_t \sin 2\vartheta \rangle_{\mathbf{k}}^2}{\det M_1}, \qquad (15) \end{aligned}$$

where the last line is derived using D'_- determined by Eq. (10). Note that Eq. (15) includes $\det M_1$ in the denominator. This implies that a resonance EM absorption due to the clapping mode occurs at the eigen frequency. To see this explicitly, it is useful to estimate the real part σ_1 by assuming the long wavelength condition such that $v_{\mathrm{F}} q \ll \Delta$. This assumption is justified for type II superconductors, since the penetration depth λ is large compared with the coherence length ξ_0 and the important values of q in the Fourier integral of the fields penetrating into the superconductor are $\lesssim \lambda^{-1}$. In what follows, we discuss the ω-dependence of σ_1 in this case.

Since we are interested in high frequencies $\omega \sim \Delta$, we may expand the conductivity in terms of q. Expanding Eqs. (14) and (15) up to the order q^2 and adding the results, we obtain

$$\sigma_t(\mathbf{q},\omega) = \frac{ine^2 v_{\mathrm{F}}^2 q^2}{4m\omega^3}\left(1 - \mathcal{F}_0 \frac{\omega^2 - 4\Delta^2}{\omega^2 - \omega_{\mathrm{cl}}^2}\right) + \sigma_t^{\mathrm{dia}}, \qquad (16)$$

where $\mathcal{F}_0 = \Delta^2 \mathcal{F}(\mathbf{q}=0,\omega)$. Equation (16) clearly shows that σ_t has a pole at the eigen frequency of the clapping mode, yielding a delta function peak in the real part σ_1. The diamagnetic term σ_t^{dia} in Eq. (16) is pure imaginary except at $\omega = 0$, so that only the first term contributes to σ_1 at the high frequencies of interest.

We briefly discuss σ_1 in the low frequency region $\omega \ll \Delta$ where the OPCM does not come into play. There are two contributions to σ_1 at the low frequencies. One is a delta function at $\omega = 0$, associated with superfluid motion excited by EM fields. The other is caused by thermally excited quasiparticles. The energy conservation $\omega = |E_{\mathbf{k}_+} - E_{\mathbf{k}_-}|$ for the corresponding quasiparticle-scattering process requires that this contribution is restricted in the region $\omega < v_{\mathrm{F}} q \ll \Delta$. We note that in the limit $v_{\mathrm{F}} q/\Delta \to 0$, the conductivity sum rule $\int_0^\infty d\omega \sigma_1(\mathbf{q},\omega) = \pi ne^2/2m$ is satisfied only by the two contributions. As can be shown from Eq. (14), in the limit $v_{\mathrm{F}} q/\Delta \to 0$, the ω-integration yields $\pi n_s e^2/2m$ for the $\delta(\omega)$ term and $\pi n_n e^2/2m$ for the contribution from thermally excited quasiparticles, where n_s is the superfluid density and $n_n = n - n_s$ is the normal-fluid density. This explains why σ_1 at $\omega \sim \Delta$, given by Eq. (16), is proportional to q^2.

Equation (16) depends on temperature T through $\mathcal{F}_0$ and Δ. At sufficiently low temperatures, the hyperbolic tangent function, $\tanh(E_{\mathbf{k}}/2T)$, in $\mathcal{F}_0$ may be replaced by unity; then Eq. (16) is reduced to the result for $T = 0$. Figure 1 shows the ω-dependence of the real part σ_1 at $T = 0$ obtained from Eq. (16). The structure above $\omega = 2\Delta$ is caused by pair-breaking processes. Below the pair-breaking edge, $\omega < 2\Delta$, there is a delta function peak at $\omega_{\mathrm{cl}} = \sqrt{2}\Delta$, associated with the absorption of the clapping mode. This collective-mode contribution is explicitly given by $\sigma_1^{\rm cm}(\mathbf{q},\omega) = (\pi^2 ne^2 v_{\rm F}^2 q^2/64m\Delta^2)\delta(\omega-\omega_{\rm cl})$.

Hirschfeld *et al.*[8] have studied the power absorption from the OPCM in the Balian-Werthamer state (in a 3D system). The power absorption $P(\omega)$ is given as the dissipation of the field energy which appears as Joule heat. To consider $P(\omega)$, we need to take into account the presence of the vacuum-metal interface. They estimated $P(\omega)$ by assuming the specular surface boundary condition and by neglecting the surface scattering effect causing the pair breaking near the surface. In the 2D $k_x \pm ik_y$ state considered here, the same calculation is repeated by using Eq. (16) and considering the EM wave injected along the 2D plane. The resulting collective-mode contribution to $P(\omega)$ has the following ω-dependence: $P^{\rm cm}(\omega) = 0$ below $\omega = \omega_{\rm cl}(0)$. Above the threshold, $\omega > \omega_{\rm cl}(0)$, $P^{\rm cm}(\omega)$ increases rapidly with ω and then has a peak structure with a finite width $\sim (\xi_0/\lambda_L)\Delta$ ($\lambda_L = (mc^2/4\pi ne^2)^{1/2}$, the London penetration depth); this ω-dependence is descried by $P^{\rm cm}(\omega) \sim [\omega^2-\omega_{\rm cl}^2(0)]^{1/2}/[\omega^2-\omega_{\rm cl}^2(0)+c_1^2\lambda_L^{-2}]^2$, where $c_1 = v_{\rm F}/\sqrt{2}$ is the velocity determining the dispersion of the clapping mode. In the power absorption spectrum, the OPCM gives rise to not a delta function peak but a broadened peak. This is a consequence of taking into account the dispersion of $\omega_{\rm cl}$ in the denominator of Eq. (16). In actual metals, impurity scattering also brings about the broadening. The power absorption spectrum, however, has a definite peak structure due to the collective excitation if ξ_0 is small enough compared with λ_L and at least the superconductor is clean. This demonstrates that the clapping mode in the $k_x \pm ik_y$-wave type II superconductor can be observed by EM absorption measurements.

---

[1] Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz and F. Lichtenberg, Nature **372**, 532 (1994).

[2] T. M. Rice and M. Sigrist, J. Phys. Condens. Matter **7**, L643 (1995).

[3] K. Ishida, Y. Kitaoka, K. Asayama, S. Ikeda, S. Nishizaki, Y. Maeno, K. Yoshida and T. Fujita, Phys. Rev. B **56**, R505 (1997).

[4] A. P. Mackenzie, R. K. W. Haselwimmer, A. W. Tyler, G. G. Lonzarich, Y. Mori, S. Nishizaki and Y. Maeno, Phys. Rev. Lett. **80**, 161 (1998).

[5] G. M. Luke, Y. Fudamoto, K. M. Kojima, M. I. Larkin, J. Merrin, B. Nachumi, Y. J. Uemura, Y. Maeno, Z. Q. Mao, Y. Mori, H. Nakamura and M. Sigrist, Nature **394**, 558 (1998).

[6] K. Ishida, H. Mukuda, Y. Kitaoka, K. Asayama, Z. Q. Mao, Y. Mori and Y. Maeno, Nature **396**, 658 (1998).

[7] D. S. Hirashima and H. Namaizawa, Prog. Theor. Phys. **77**, 563 (1987); Prog. Theor. Phys. **77**, 585 (1987).

[8] P. J. Hirschfeld, P. Wölfle, J. A. Sauls, D. Einzel and W. O. Putikka, Phys. Rev. B **40**, 6695 (1989).

[9] L. Tewordt, Phys. Rev. Lett. **83**, 1007 (1999).

[10] L. Tewordt, J. Low Temp. Phys. **117**, 1 (1999).

[11] We note that in the chiral p-wave superconductor like the $k_x \pm ik_y$ superconductor, the correction term arising from the q-dependence of $\Delta_{\mathbf{k}\pm}$ yields an unusual Hall current discussed by Goryo and Ishikawa [J. Goryo and K. Ishikawa, J. Phys. Soc. Jpn. **67**, 3006 (1998); Phys. Lett. A **260**, 294 (1999)].

[12] D. Vollhardt and P. Wölfle, *The Superfluid Phases of Helium 3* (Taylor & Francis, 1990).

[13] P. Wölfle, Phys. Rev. Lett. **37**, 1279 (1976).

[14] H. Matsui, M. Yamaguchi, Y. Yoshida, A. Mukai, R. Settai, Y. Ōnuki, H. Takei and N. Toyota, J. Phys. Soc. Jpn. **67**, 3687 (1998).

[15] T. Oguchi, Phys. Rev. B **51**, 1385 (1995).

[16] A. P. Mackenzie, S. R. Julian, A. J. Diver, G. J. McMullan, M. P. Ray, G. G. Lonzarich, Y. Maeno, S. Nishizaki and T. Fujita, Phys. Rev. Lett. **76**, 3786 (1996).

FIG. 1. Real part $\sigma_1(\mathbf{q},\omega)$ of the complex conductivity at $T=0$ as a function of reduced frequency ω/Δ. The ordinate is scaled by $ne^2v_{\rm F}^2q^2/m\Delta^3$. A delta function peak at the eigen frequency of the clapping mode, $\omega/\Delta = \sqrt{2}$, is plotted as a Lorentzian with a tiny width.

TABLE I. Order parameter collective modes of the k_x+ik_y state in the long wavelength limit $q \to 0$.

Variable	Eigen frequency	Mode
D'_+	2Δ	
D''_+	0	Anderson-Bogoliubov mode
D'_-, D''_-	$\sqrt{2}\Delta$	Clapping mode

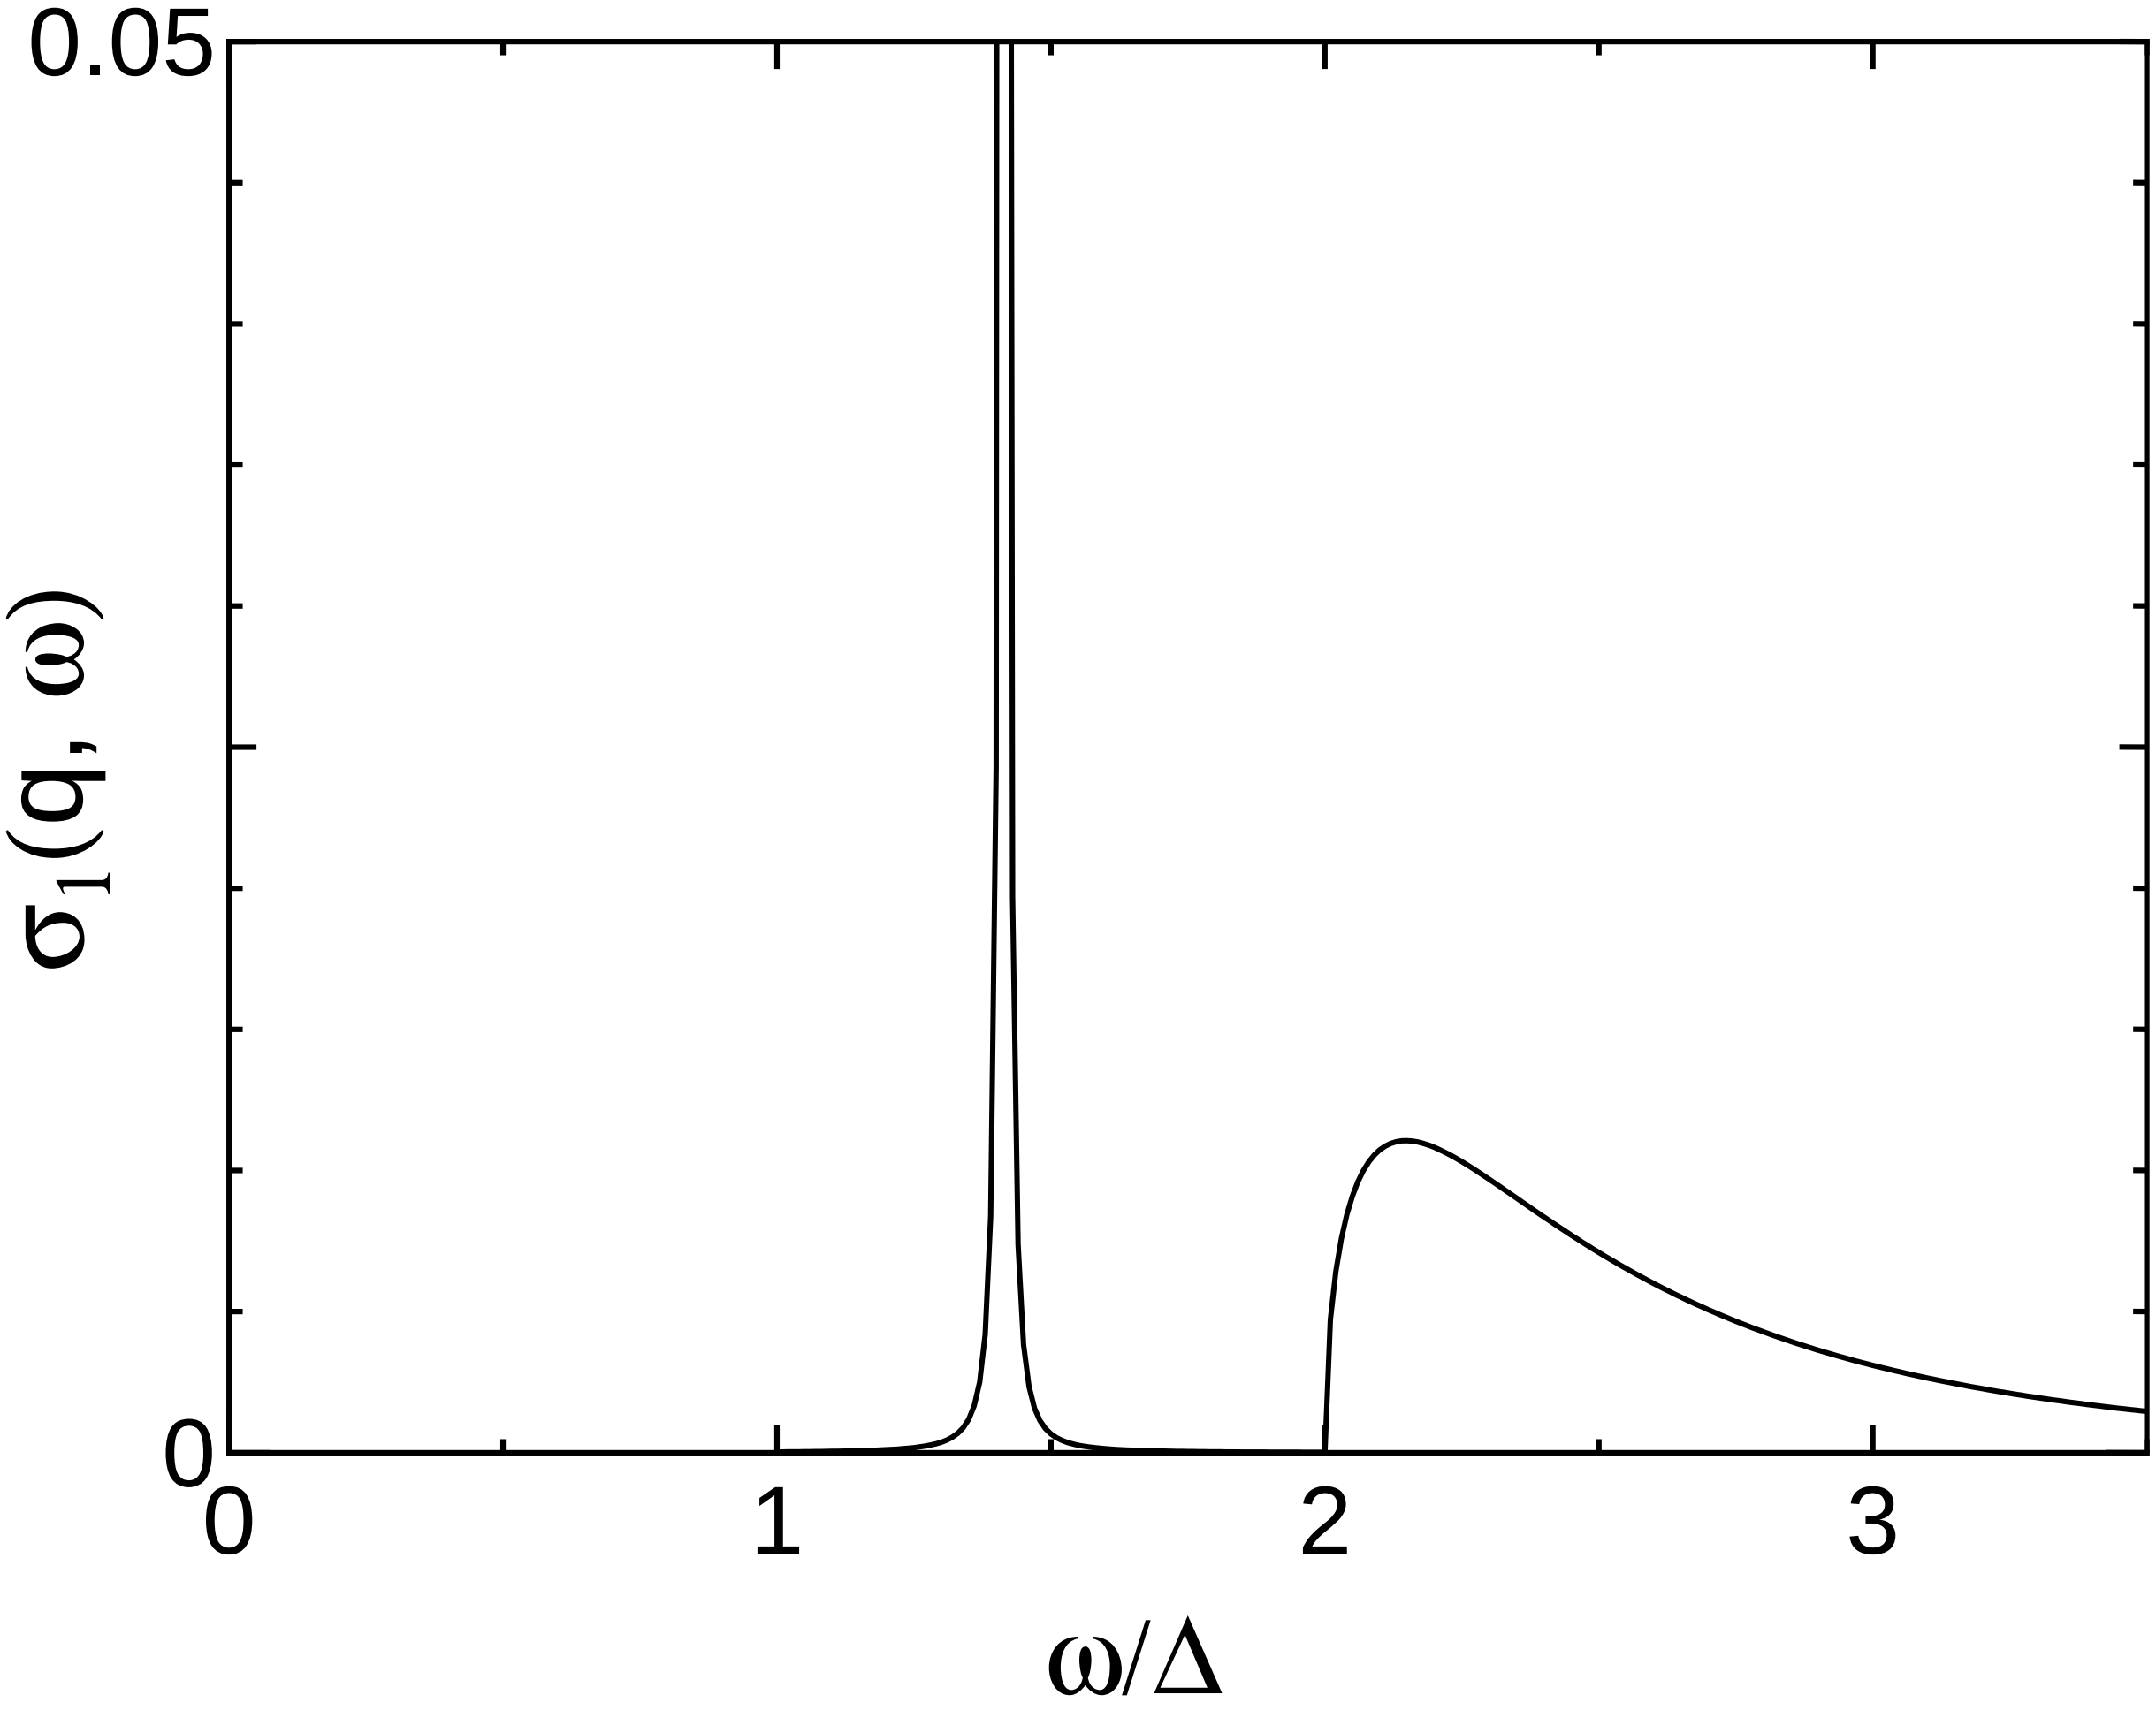
0.05
0
σ₁(q, ω)
0
1
2
3
ω/Δ